

A.U. Abuova<sup>1</sup>, T.M. Inerbaev<sup>1,2</sup>, F.U. Abuova<sup>1\*</sup>, G.A. Kaptagay<sup>3</sup>

<sup>1</sup>*L.N. Gumilyov Eurasian National University, Nur-Sultan, Kazakhstan;*

<sup>2</sup>*South China Normal University, Guangzhou, China;*

<sup>3</sup>*Kazakh National Women's Teacher Training University, Almaty, Kazakhstan  
(E-mail: Fatika\_82@mail.ru)*

## Theoretical study of the Ni–C system in the pressure range of 0–100 GPa

This work is devoted to the search for stable compounds and structures in the Ni–C system in the pressure range of 0–100 GPa. Based on the density functional theory, a search for stable compounds and structures in the Ni–C system was carried out using modern algorithms for predicting crystal structures. As a result, one stable intermediate compound Ni<sub>3</sub>C with the structure of cementite, previously synthesized at 184 GPa, was revealed. Ni<sub>3</sub>C nickel carbide is dynamically stable, which is confirmed by the absence of imaginary modes in the phonon spectra. According to the results obtained, Ni<sub>3</sub>C is formed by the reaction of  $3\text{Ni} + \text{C} \leftrightarrow \text{Ni}_3\text{C}$  above 23 GPa and is stable up to at least 100 GPa. Spin-polarized calculations showed that the Ni<sub>3</sub>C has no magnetic moment in the entire pressure range. For carbon-rich compounds, performed calculations on the crystal structure prediction did not reveal any phase that would be energetically favorable relative to a mixture of pure nickel and carbon. Also, it was shown that the most energetically favorable modification of metastable carbide Ni<sub>7</sub>C<sub>3</sub> is orthorhombic Ni<sub>7</sub>C<sub>3</sub>-Pbca.

*Keywords:* density functional theory, crystal structure prediction, USPEX, AIRSS, high pressure, phase stability, phonon spectra, nickel carbide.

### Introduction

The Ni–C system at high pressure is of interest both from the point of view of Earth sciences and materials science. Nickel carbides are of active interest as catalysts in the chemical deposition of a gas mixture (CVD) to produce high-quality graphene [1]. In addition, nanoparticles of metal carbides, particularly nickel, in the carbon matrix make up nanocomposite thin films, which have a wide profile of application in metallurgy [2]. On the other hand, nickel is the second most common element in the Earth's core after iron [3]. According to cosmochemical data, the core contains 5 wt.% Ni [4]. However, seismic observations show that the core density is significantly lower than that of pure Fe and Fe–Ni alloy under P–T core conditions [5], which suggests the presence of a light element in the core. The question “what exactly are these elements, and what is their number?” remains the subject of active discussions today. Recent estimates of the composition of the inner core indicate a carbon content of up to 2.0 wt.% [4], which makes it a potential candidate for the role of a light element in the Earth's core. Therefore, to study the composition and structure of the Earth's core, it is important to investigate the Fe–Ni–C system at high pressures. To study the ternary Fe–Ni–C system, first, the binary Fe–C and Ni–C systems should be investigated. In the last decade, the Fe–C system has been actively studied at high pressure both theoretically and experimentally [6–9]. To date, there is only one experimental work [10] on the Ni–C system at high pressure and there is no theoretical study on this system. Thus, it is considerable to carry out theoretical study on the Ni–C system.

There are no stable binary Ni–C compounds at atmospheric pressure. In a recent work [10], it was shown that at high pressure (~184 GPa), a stable compound of Ni<sub>3</sub>C with the structure of cementite (Fe<sub>3</sub>C) is formed. To date, this is the only known stable compound in the Ni–C system.

This work is devoted to the search for stable compounds and structures in the Ni–C system in the pressure range of 0–100 GPa.

### Experimental

Calculations implemented by authors on licensed USPEX and AIRSS software allow calculating the electronic structure of periodic systems with the use of the density functional theory.

The search for stable crystal structures in the Ni–C system was carried out using evolutionary algorithms and the random sampling method implemented in the USPEX and AIRSS software packages at pressures of 0, 25, 50, and 100 GPa. The search was conducted using the variable composition method and the USPEX code, while the structures were generated by the AIRSS code for fixed compositions, namely the carbon-enriched part of the Ni–C system.

The number of structures of the initial generation in the calculations by the USPEX method was equal to 50. After their optimization, 60% of the structures with the lowest enthalpy were selected, which were used to generate a new generation in the following percentage ratio: by heredity – 35%, by atomic mutations – 20%, by permutation of lattice parameters – 10% and 35% of all structures of the new generation were generated randomly. In the case of calculations of AIRSS methods, 2000–3200 structures were randomly generated and optimized, from which the most energetically favorable structures were selected. In all calculations, optimization was performed within the framework of density functional theory (DFT), using the conjugate gradient algorithm. The optimization parameters were as follows: the cutting energy of the plane wave basis was 450 eV, the Monkhorst-Pack k-point grid [11] with a point density equal to  $0.5 \text{ \AA}^{-1}$ , the electronic blur was according to the Methfessel-Paxton scheme [12], the parameter  $\sigma = 0.05 \text{ eV}$ . Calculations of the ground state energies of the most promising of the predicted structures were conducted within the framework of the density functional theory (DFT) by the pseudo potentials method, in the VASP 5.3 software package [13, 14] with higher accuracy: the cut-off energy is 600 eV, the density of k-points is  $0.2 \text{ \AA}^{-1}$ , the parameter  $\sigma = 0.1 \text{ eV}$ . The exchange-correlation interaction was taken into account in the approximation of the generalized gradient according to the Perdew-Burke-Ernzerhof (PBE) scheme [15].

To calculate the phonon spectra, the lattice dynamics method was used in the framework of the quasi-harmonic approximation in the PHONOPY software package [16].

### Results and Discussion

Using modern methods of structure prediction, the only energetically advantageous compound  $\text{Ni}_3\text{C}$  was found, as well as a number of metastable structures  $\text{NiC}$ ,  $\text{NiC}_2$ , and  $\text{NiC}_3$  (Fig. 1).  $\text{Ni}_3\text{C}$  stabilizes in the cementite structure (Pnma) above 23 GPa relative to the reaction  $3\text{Ni} + \text{C} \leftrightarrow \text{Ni}_3\text{C}$  (Figure 2a). The most favorable among the predicted structures of the remaining compounds turned out to be energetically unfavorable relative to a mixture of pure nickel and carbon in the entire studied pressure range (0–100 GPa), with  $\Delta H$  reaching values of 0.4 eV/f.u. for  $\text{NiC}$ ,  $\text{NiC}_2$ , and  $\text{NiC}_3$  (Figure 1). In the Fe–C system, in addition to  $\text{Fe}_3\text{C}$ ,  $\text{Fe}_7\text{C}_3$  is also thermodynamically stable.  $\text{Fe}_7\text{C}_3$  iron carbide has two stable modifications:  $\text{Fe}_7\text{C}_3\text{-Pbca}$  and  $\text{Fe}_7\text{C}_3\text{-P63mc}$ . Similarly,  $\text{Ni}_7\text{C}_3$  nickel carbide was also considered in the form of two modifications. The structural models  $\text{Ni}_7\text{C}_3\text{-Pbca}$  and  $\text{Ni}_7\text{C}_3\text{-P63mc}$  were constructed by replacing all iron atoms with nickel atoms in the structures  $\text{Fe}_7\text{C}_3\text{-Pbca}$  and  $\text{Fe}_7\text{C}_3\text{-P63mc}$  [17]. The calculation of the ground state energy of the obtained structures showed that  $\text{Ni}_7\text{C}_3\text{-Pbca}$  is an energetically more favorable structure than  $\text{Ni}_7\text{C}_3\text{-P63mc}$  by  $\sim 0.42 \text{ eV/f.u.}$ , however, it is energetically less favorable relative to the mechanical mixture of  $7/3\text{Ni}_3\text{C} + 2/3\text{C}$  in the entire pressure range considered (Fig. 2b).

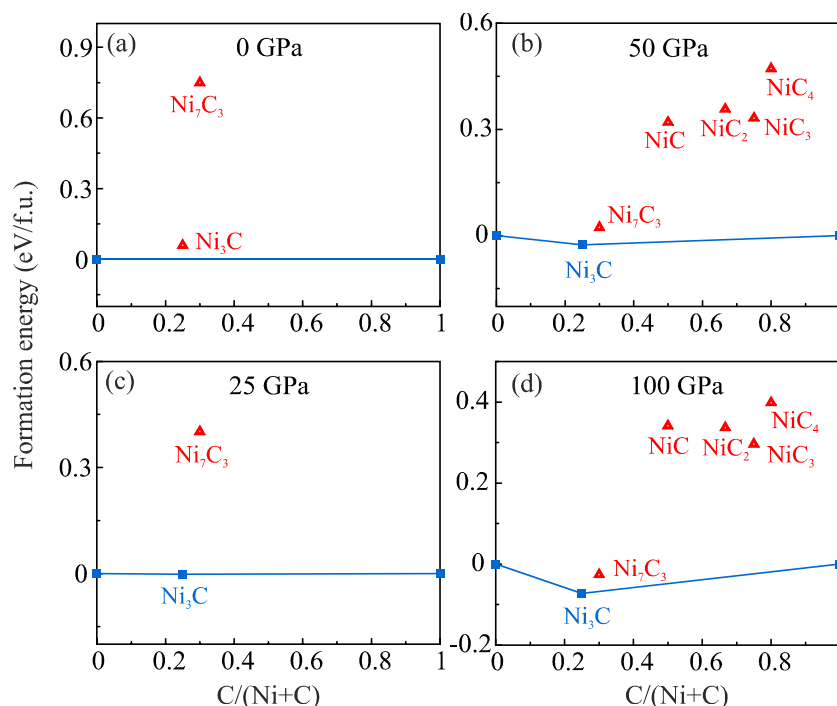


Figure 1. Thermodynamic convex hulls at various pressures and temperatures of 0 K

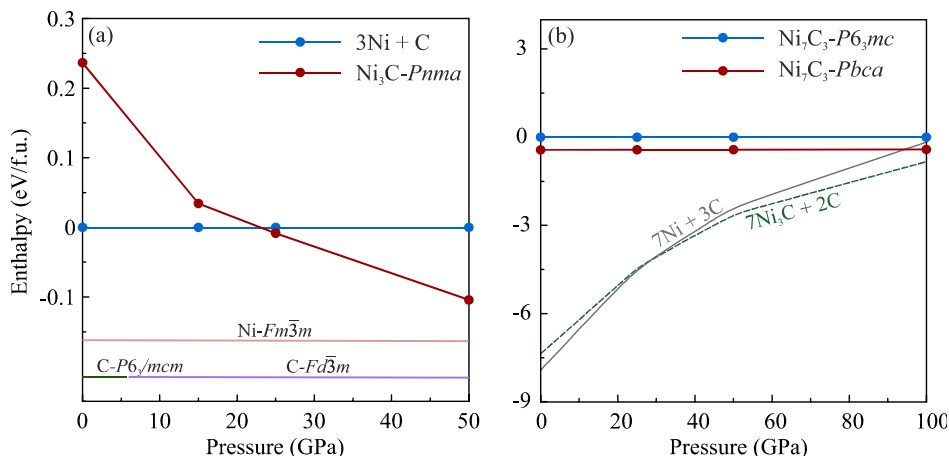


Figure 2. The dependence of the enthalpy on the pressure of  $\text{Ni}_3\text{C}$ – $\text{Pnma}$  with respect to the decomposition reaction to the association of  $3\text{Ni} + \text{C}$  (a) and the dependence of the enthalpy on the pressure for modifications of  $\text{Ni}_7\text{C}_3$  with the application of possible decomposition reactions (b)

Spin-polarized calculations showed the absence of a magnetic moment in the entire studied pressure range. According to the calculations of the phonon dispersion curves,  $\text{Ni}_3\text{C}$  at 25 GPa is characterized by the presence of only real modes, which indicates the dynamic stability of this phase (Fig. 3).

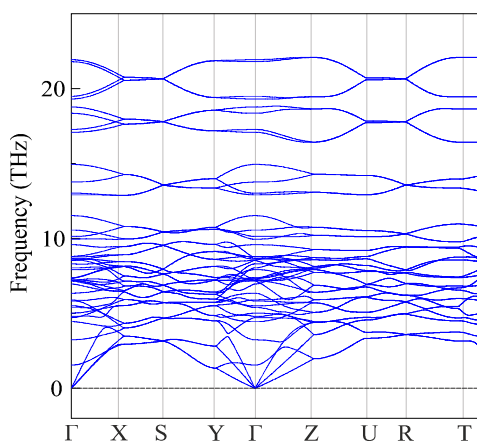


Figure 3.  $\text{Ni}_3\text{C}$ – $\text{Pnma}$  phonon spectrum at 25 GPa

Also, for comparison with the experimental data [10], the equation of state in the range of 0–200 GPa was calculated. It can be seen from Figure 4 and Table 1 that our results are in good agreement with the experiment.

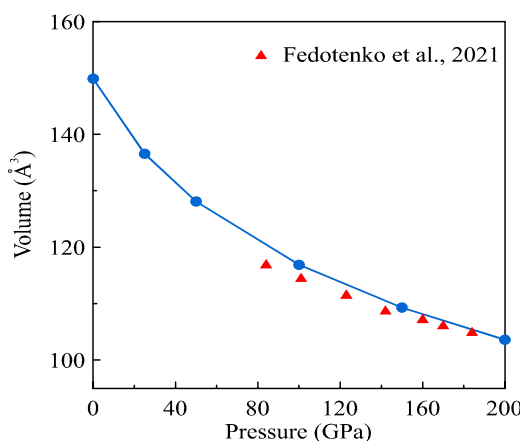


Figure 4. Pressure-volume dependence for  $\text{Ni}_3\text{C}$ – $\text{Pnma}$

Calculated parameters  $V_0$  and  $K_0$  in comparison with experimental data [10]

	$V_0$ ( $\text{\AA}^3$ )	$K_0$ (ГПа)
Experiment	147,7(8)	157(10)
This work	149,88	168

*Conclusions*

Within the scope of this study, a search for stable structures in the Ni–C system was carried out. It was shown that the Ni–C system in the pressure range of 0–100 GPa is characterized by one intermediate compound NiC. This nickel carbide is stabilized relative to the mechanical mixture of Ni and C above 23 GPa. The dynamic stability of Ni<sub>3</sub>C is confirmed by the absence of imaginary frequencies in the phonon spectrum. Also, for comparison with experimental data, the Ni<sub>3</sub>C equation of state was calculated in the pressure range of 0–200 GPa. The obtained result is in good agreement with the experiment.

*Acknowledgments*

This work was carried out within the framework of the grant project AP09562464 “Search for functional (superhard) materials in Ni–B, Ni–C and Ni–N systems” for 2021 of the Ministry of Education and Science of the Republic of Kazakhstan.

## References

- Hofmann S. CVD-enabled graphene manufacture and technology / S. Hofmann, P. Braeuninger-Weimer, R.S. Weatherup // The journal of physical chemistry letters. — 2015. — Vol. 6, No. 14. — P. 2714–2721. DOI: 10.1021/acs.jpcllett.5b01052
- Bayer B.C. In situ observations of phase transitions in metastable nickel (carbide)/carbon nanocomposites / B.C. Bayer, D.A. Bosworth, F.B. Michaelis, R. Blume, G. Habler, R. Abart, R.S. Weatherup, P.R. Kidambi, J.J. Baumberg, A. Knop-Gericke // The Journal of Physical Chemistry C. — 2016. — Vol. 120, No. 39. — P. 22571–22584. DOI: 10.1021/acs.jpcc.6b01555
- Birch F. Elasticity and constitution of the Earth's interior / F. Birch // Journal of Geophysical Research. — 1952. — Vol. 57, No. 6. — P. 227–286. DOI: 10.1029/JZ057i002p00227
- Litasov K.D. Composition of the Earth's core: A review / K.D. Litasov, A. Shatskiy // Russian Geology and Geophysics. — 2016. — Vol. 57, No. 1. — P. 22–46. DOI: 10.15372/GiG20160103
- Stevenson D.J. Models of the Earth's Core / D.J. Stevenson // Science. — 1981. — Vol. 214 (4521). — P. 611–619. DOI: 10.1126/science.214.4521.611
- Bazhanova Z.G. Fe–C and Fe–H systems at pressures of the Earth's inner core / Z.G. Bazhanova, A.R. Oganov, O. Gianola // Physics-Uspokhi. — 2012. — Vol. 55, No. 5. — P. 489–497. DOI: 10.3367/UFNe.0182.201205.c.0521
- Litasov K.D. Thermal expansion of iron carbides, Fe<sub>7</sub>C<sub>3</sub> and Fe<sub>3</sub>C, at 297–911 K determined by in situ X-ray diffraction / K.D. Litasov, S.V. Rashchenko, A.N. Shmakov, Y.N. Palyanov, A.G. Sokol // Journal of Alloys and Compounds. — 2015. — Vol. 628. — P. 102–106. DOI: 10.1016/j.jallcom.2014.12.138
- Prescher C. High Poisson's ratio of Earth's inner core explained by carbon alloying / C. Prescher, L. Dubrovinsky, E. Bykova, I. Kuzenko, K. Glazyrin, A. Kantor, C. McCammon, M. Mookherjee, Y. Nakajima, N. Miyajima // Nature Geoscience. — 2015. — Vol. 8, No. 3. — P. 220. DOI: 10.1038/ngeo2370
- Weerasinghe G.L. Computational searches for iron carbide in the Earth's inner core / G.L. Weerasinghe, R. Needs, C.J. Pickard // Physical Review B. — 2011. — Vol. 84, No. 17. — P. 174110. DOI: 10.1103/PhysRevB.84.174110
- Fedotenko T. Synthesis and Compressibility of Novel Nickel Carbide at Pressures of Earth's Outer Core / T. Fedotenko, S. Khandarkhaeva, L. Dubrovinsky, K. Glazyrin, P. Sedmak, N. Dubrovinskaja // Minerals. — 2012. — Vol. 11, No. 5. — P. 516. DOI: 10.3390/min11050516
- Monkhorst H.J. Special points for Brillouin-zone integrations / H.J. Monkhorst, J.D. Pack // Physical review B. — 1976. — Vol. 13, No. 12. — P. 5188. DOI: 10.1103/PhysRevB.13.5188
- Methfessel M. High-precision sampling for Brillouin-zone integration in metals / M. Methfessel, A. Paxton // Physical Review B. — 1989. — Vol. 40, No. 6. — P. 3616. DOI: 10.1103/physrevb.40.3616
- Kresse G. Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set / G. Kresse, J. Furthmüller // Computational Materials Science. — 1996. — Vol. 6 (1). — P. 15–50. DOI: 10.1016/0927-0256(96)00008-0
- Kresse G. From ultrasoft pseudopotentials to the projector augmented-wave method / G. Kresse, D. Joubert // Physical Review B. — 1999. — Vol. 59, No. 3. — P. 1758. DOI: 10.1103/PhysRevB.59.1758
- Perdew J.P. Generalized gradient approximation made simple / J.P. Perdew, K. Burke, M. Ernzerhof // Physical review letters. — 2015. — Vol. 77, No. 18. — P. 3865. DOI: 10.1103/PhysRevLett.77.3865

16 Togo A. First principles phonon calculations in materials science / A. Togo, I. Tanaka // *Scripta Materialia*. — 2015. — Vol. 108. — P. 1–5. DOI: 10.1016/j.scriptamat.2015.07.021

17 Sagatov N. New high-pressure phases of  $\text{Fe}_7\text{N}_3$  and  $\text{Fe}_7\text{C}_3$  stable at Earth's core conditions: evidences for carbon–nitrogen isomorphism in Fe-compounds / N. Sagatov, P.N. Gavryushkin, T.M. Inerbaev, K.D. Litasov // *RSC Advances*. — 2019. — Vol. 9, No. 7. — P. 3577–3581. DOI: 10.1039/C8RA09942A

А.У. Абуова, Т.М. Инербаев, Ф.У. Абуова, Г.А. Каптагай

## 0–100 ГПа қысым диапазонындағы Ni–C жүйесін теориялық зерттеу

Мақала 0–100 ГПа қысым диапазонында Ni–C жүйесіндегі тұрақты қосылыстар мен құрылымдарды іздеуге арналған. Тығыздықтың функционалды теориясының негізінде Ni–C жүйесінде кристалдық құрылымдарды болжаудың заманауи алгоритмдерін пайдалана отырып, тұрақты қосылыстар мен құрылымдар іздестірілді. Нәтижесінде бұрын 184 ГПа синтезделген цементит құрылымымен бір тұрақты  $\text{Ni}_3\text{C}$  аралық байланыс табылды.  $\text{Ni}_3\text{C}$  никель карбиді динамикалық тұрақты, бұл фондық спектрлерде қиялық модасының болмауымен расталады. Алынған нәтижелерге сәйкес,  $\text{Ni}_3\text{C}$   $3\text{Ni} + \text{C} \leftrightarrow \text{Ni}_3\text{C}$  23 ГПа-дан жоғары реакция нәтижесінде пайда болады және кем дегенде 100 ГПа-ға дейін тұрақты болады. Айналдыру поляризациясымен есептеулер  $\text{Ni}_3\text{C}$ -де қысымның барлық диапазонында магниттік момент жоқ екенін көрсетті. Көміртекке бай қосылыстар үшін кристалдық құрылымды болжау бойынша есептеулер таза никель мен көміртегі қоспасымен салыстырғанда энергетикалық жағынан қолайлы болатын бірде-бір фазаны анықтаған жоқ. Сондай-ақ,  $\text{Ni}_7\text{C}_3$  метастабильді карбидтің ең энергетикалық тиімді модификациясы орторомбиялық  $\text{Ni}_7\text{C}_3$ -Pbca екендігі көрсетілген.

*Кілт сөздер:* тығыздықтың функционалды теориясы, кристалды құрылымды болжау, USPEX, AIRSS, жоғары қысым, фазалық тұрақтылық, фондық спектрлер, никель карбиді.

А.У. Абуова, Т.М. Инербаев, Ф.У. Абуова, Г.А. Каптагай

## Теоретическое исследование системы Ni–C в диапазоне давлений 0–100 ГПа

Статья посвящена поиску стабильных соединений и структур в системе Ni–C в диапазоне давлений 0–100 ГПа. На основе теории функционала плотности был проведен поиск стабильных соединений и структур в системе Ni–C с использованием современных алгоритмов прогнозирования кристаллических структур. В результате было обнаружено одно стабильное промежуточное соединение  $\text{Ni}_3\text{C}$  со структурой цементита, ранее синтезированное при 184 ГПа. Карбид никеля  $\text{Ni}_3\text{C}$  динамически стабилен, что подтверждается отсутствием воображаемых мод в фонных спектрах. Согласно полученным данным,  $\text{Ni}_3\text{C}$  образуется в результате реакции  $3\text{Ni} + \text{C} \leftrightarrow \text{Ni}_3\text{C}$  выше 23 ГПа и стабилен по меньшей мере до 100 ГПа. Расчеты со спиновой поляризацией показали, что  $\text{Ni}_3\text{C}$  не имеет магнитного момента во всем диапазоне давлений. Для соединений, богатых углеродом, проведенные расчеты по прогнозированию кристаллической структуры не выявили ни одной фазы, которая была бы энергетически благоприятной по сравнению со смесью чистого никеля и углерода. Также было показано, что наиболее энергетически выгодной модификацией метастабильного карбида  $\text{Ni}_7\text{C}_3$  является орторомбический  $\text{Ni}_7\text{C}_3$ -Pbca.

*Ключевые слова:* теория функционала плотности, предсказание кристаллической структуры, USPEX, AIRSS, высокое давление, фазовая стабильность, фонные спектры, карбид никеля.

## References

- Hofmann, S., Braeuninger-Weimer, P. & Weatherup, R.S. (2015). CVD-enabled graphene manufacture and technology. *The journal of physical chemistry letters*, 6, No. 14, 2714–2721. DOI: 10.1021/acs.jpcclett.5b01052
- Bayer, B.C., Bosworth, D.A., Michaelis, F.B., Blume, R., Habler, G., Abart, R., & et al. (2016). In situ observations of phase transitions in metastable nickel (carbide)/carbon nanocomposites. *The Journal of Physical Chemistry C*, 120, No. 39, 22571–22584. DOI: 10.1021/acs.jpcc.6b01555
- Birch, F. (1952). Elasticity and constitution of the Earth's interior. *Journal of Geophysical Research*, 57, No. 6, 227–286. DOI: 10.1029/JZ057i002p00227
- Litasov, K.D. & Shatskiy, A. (2016). Composition of the Earth's core: A review. *Russian Geology and Geophysics*, 57, No. 1, 22–46. DOI: 10.15372/GiG20160103
- Stevenson, D.J. (1981). Models of the Earth's Core. *Science*, 214 (4521), 611–619. DOI: 10.1126/science.214.4521.611

- 6 Bazhanova, Z.G., Oganov, A.R. & Gianola, O. (2012). Fe–C and Fe–H systems at pressures of the Earth's inner core. *Physics-Uspokhi*, 55, No. 5, 489–497. DOI: 10.3367/UFNe.0182.201205 c.0521
- 7 Litasov, K.D., Rashchenko, S.V., Shmakov, A.N., Palyanov, Y.N., & Sokol, A.G. (2015). Thermal expansion of iron carbides, Fe<sub>7</sub>C<sub>3</sub> and Fe<sub>3</sub>C, at 297–911 K determined by in situ X-ray diffraction. *Journal of Alloys and Compounds*, 628, 102–106. DOI: 10.1016/j.jallcom.2014.12.138
- 8 Prescher, C., Dubrovinsky, L., Bykova, E., Kuppenko, I., Glazyrin, K., Kantor, A., & et al. (2015). High Poisson's ratio of Earth's inner core explained by carbon alloying. *Nature Geoscience*, 8, No. 3, DOI: 10.1038/ngeo2370
- 9 Weerasinghe, G.L., Needs, R. & Pickard, C.J. (2011). Computational searches for iron carbide in the Earth's inner core. *Physical Review B*, 84, No. 17, 174110. DOI: 10.1103/PhysRevB.84.174110
- 10 Fedotenko, T., Khandarkhaeva, S., Dubrovinsky, L., Glazyrin, K., Sedmak, P., & Dubrovinskaia, N. (2012). Synthesis and Compressibility of Novel Nickel Carbide at Pressures of Earth's Outer Core. *Minerals*, 11, No. 5, 516. DOI: 10.3390/min11050516
- 11 Monkhorst, H.J. & Pack, J.D. (1976). Special points for Brillouin-zone integrations, *Physical review B*, 13, No. 12, 5188. DOI: 10.1103/PhysRevB.13.5188
- 12 Methfessel, M. & Paxton, A. (1989). High-precision sampling for Brillouin-zone integration in metals. *Physical Review B*, 40, No. 6, 3616. DOI: 10.1103/physrevb.40.3616
- 13 Kresse, G., Joubert, D. & Furthmüller, J. (1996). Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Computational Materials Science*, 6(1), 15–50. DOI: 10.1016/0927-0256(96)00008-0
- 14 Kresse, G. (1999). From ultrasoft pseudopotentials to the projector augmented-wave method. *Physical Review B*, 59, No. 3, 1758. DOI: 10.1103/PhysRevB.59.1758
- 15 Perdew, J.P., Burke, K. & Ernzerhof, M. (2015). Generalized gradient approximation made. *Physical review letters*, 77, No. 18, 3865. DOI: 10.1103/PhysRevLett.77.3865
- 16 Togo, A. & Tanaka, I. (2015). First principles phonon calculations in materials science. *Scripta Materialia*, 108, 1–5. DOI: 10.1016/j.scriptamat.2015.07.021
- 17 Sagatov, N., Gavryushkin P.N., Inerbaev T.M., & Litasov, K.D. (2019). New high-pressure phases of Fe<sub>7</sub>N<sub>3</sub> and Fe<sub>7</sub>C<sub>3</sub> stable at Earth's core conditions: evidences for carbon–nitrogen isomorphism in Fe-compounds. *RSC Advances*, 9, No. 7, 3577–3581. DOI: 10.1039/C8RA09942A